

# MAPE

MULTIDISCIPLINARY ASPECTS  
OF PRODUCTION ENGINEERING

Proceedings of XV International Conference  
**Multidisciplinary Aspects  
of Production Engineering**

VOLUME 1  
ISSUE 1


**PANOVA**  
WYDAWNICTWO

**ISBN 978-83-65265-25-8**

# **XV INTERNATIONAL CONFERENCE**

**MULTIDISCIPLINARY ASPECTS  
OF PRODUCTION ENGINEERING**

## **MAPE 2018**

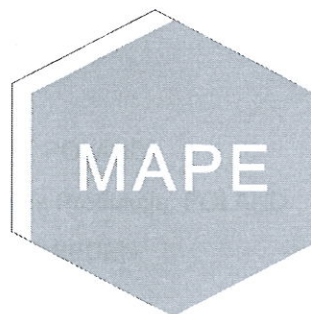

**Conference proceedings**  
volume 1  
issue 1

**05-08 september 2018, Zawiercie, Poland**

**PANOV**  
WYDAWNICTWO

This book contains complete papers approved by the Conference Scientific Committee.  
Authors are responsible for the content and accuracy.

Opinions expressed may not necessarily reflex the position of the Scientific Committee  
and Organizers of MAPE.

No part of this book may be reproduced or transmitted in any form or by any means,  
electronic or mechanical, for any purpose, without the express written permission of the  
Publisher.

Copyright © Wydawnictwo PANOVA

All Rights Reserved by Wydawnictwo PANOVA

Total print: 250

**ISBN 978-83-65265-25-8**

## SCIENTIFIC COMMITTEE

CONTI

	Techni
Juhani ANTTILA – FINLAND	
Zbigniew BANASZAK - POLAND	
Libor BENES – CZECH REPUBLIC	
Witold BIAŁY – POLAND – SCIENTIFIC SECRETARY	1
Martina BLAŠKOVÁ – SLOVAKIA	
Atul B. BORADE – INDIA	2
Otakar BOKUVKA – SLOVAKIA	
Jarosław BRODNY – POLAND	
Rostislav CHOTĚBORSKÝ – CZECH REPUBLIC	3
Edward CHLEBUS - POLAND	
Helena ČIERNÁ – SLOVAKIA	
Miroslav DRLIJACA – CROATIA	4
Marlin DYASON – GREAT BRITAIN	
Elisabeth EHRENSPERGER - SWITZERLAND	
Spilios D. FASSOIS – GREECE	5
Diego GALAR – SWEDEN	6
Józef GAWLIK - POLAND	
Rafael Barrionuevo GIMÉNEZ – SPAIN	
Magdalena GRACZYK – POLAND	7
Janusz GRABARA – POLAND	
Wiesław „Wes” GREBSKI – USA	
Armin GRUNWALD – GERMANY	8
Mario GUAGLIANO – ITALIA	
Branislav HADZIMA – SLOVAKIA	9
Adam HAMROL - POLAND	
Denis JELACIC – CROATIA	10
Dorota JELONEK – POLAND	
Jan KAŹMIERCZAK – POLAND – CHAIRMAN	11
Ryszard KNOSALA - POLAND	
Marian KUČERA – SLOVAKIA	12
Józef KUCZMASZEWSKI - POLAND	
Jiří KLIBER – CZECH REPUBLIC	13
Jerzy LEWANDOWSKI – POLAND	
Mariusz J. LIGARSKI – POLAND	14
Stephan LINGNER - GERMANY	
Andrzej LOSKA - POLAND	
Zbigniew MATUSZAK – POLAND	
Ivan MIHAJLOVIC – SERBIA	15
Ruzica NIKOLIC – SERBIA	
Frantisek NOVY – SLOVAKIA	
Joanna PALISZKIEWICZ – POLAND	16
Luminita PARV – ROMANIA	
Walter PEISSL - AUSTRIA	17
Grażyna PŁAZA – POLAND – V-CE CHAIRMAN	
Tamer RIZAOĞLU – TURKEY	18
Juraj RUŽBARSKY – SLOVAKIA	
Jasminka SAMARDŽIJA – CROATIA	
Constanze Ute SCHERZ - GERMANY	19
Eva SCHMIDOVA – CZECH REPUBLIC	
Libor SITEK – CZECH REPUBLIC	20
Bożena SKOŁUD - POLAND	
Adam TOKOR – HUNGARY	
Robert ULEWICZ – POLAND – V-CE CHAIRMAN	21
Richard VLOSKY – USA	
Ryszard WYCZÓŁKOWSKI - POLAND	
Jarosław ZAWADZKI – POLAND	
Jozef ŽARNOVSKÝ – SLOVAKIA	

## CONTENTS

### Technical Aspects of Production Engineering

1	THE USE OF TRANSFORMER MULTI-LEVEL INVERTERS IN PARALLEL OPERATION OF MARINE GENERATING SETS WITH PMSG <b>Dariusz TARNAPOWICZ</b>	3
2	SPREADING OF CRACKS DUE TO THERMAL FATIGUE IN CASE OF METAL MOLDS <b>Juraj RUŽBARSKÝ, Witold BIAŁY</b>	11
3	PROBLEMS OF FRICTION FORCE MEASUREMENT BETWEEN CYLINDRICAL OUTDOOR AND INTERNAL SLIDE PARTS <b>Jan MONIETA</b>	19
4	DETECTION AND RECORDING OF ACOUSTIC EMISSION IN DISCRETE IGBT TRANSISTORS <b>Radosław GORDON, Andrzej DREAS</b>	27
5	ANALYSIS OF CORNERS MILLING OF ALUMINUM ALLOY ELEMENTS <b>Kamil ANASIEWICZ, Maciej WŁODARCZYK</b>	33
6	THE STRUCTURAL MODEL OF THE ELECTRIC DRIVE WITH DOUBLE-FED ASYNCHRONOUS MACHINE AND DIRECT TORQUE CONTROL <b>Sergey GERMAN-GALKIN, Maciej KOZAK</b>	41
7	INFLUENCE OF PRESSURE EQUALISATION ELEMENTS ON THE QUALITY OF INSULATING GLASS UNITS <b>Zbigniew RESPONDEK</b>	47
8	IMPROVEMENT OF THE PRODUCTION PROCESS IN THE INDUSTRY 4.0 CONTEXT <b>Sandra GRABOWSKA</b>	55
9	DESIGN AND MODELING OF AN EXPERIMENTAL HYDRAULIC DEVICE <b>Zdenko TKÁČ, Marek HALENÁR, Ján KOSIBA</b>	63
10	DESIGN OF GRINDING MACHINE SPINDLE <b>Lukas RUDOLF, Jiri FRIES, Oldrich UCEN, Tomas KUBIN, Lukas KUDRNA</b>	69
11	PRACTICAL ASPECTS OF EVENT LOGS CREATION FOR INDUSTRIAL PROCESS MODELLING <b>Agnieszka TRZCIONKOWSKA, Edyta BRZYCHCZY</b>	77
12	QUALITY CONTROL IN AEROSOL PRODUCTION <b>Anna FITRZYK, Katarzyna NIEMIEC</b>	85
13	ANALYSIS OF DEVICE FAILURE IN THE MECHANICAL PRODUCTION PLANT <b>Jacek SITKO, Rastislav MIKUŠ, Pavol BOŽEK</b>	93
14	INFLUENCE OF CONSTRUCTIONAL AND KINEMATIC PARAMETERS OF THE NEW SOLUTION OF MINING HEAD ON THE EFFICIENCY OF ROADHEADER USED FOR TUNNELLING IN HARD ROCK <b>Krzysztof KOTWICA, Paweł SIENKIEWICZ</b>	101
15	LITERATURE RESEARCH IN THE FIELD OF TECHNOLOGY ASSESSMENT USING A TOOL OF A SYSTEMATIC LITERATURE REVIEW <b>Dorota PALKÁ, Jarosław BRODNY, Tamer RIZAOĞLU, Utku BAĞCI, Jozef MAŠČENÍK</b>	109
16	MEASUREMENT OF FORCES DURING THE EXTRACTION PROCESS <b>Witold BIAŁY, Jerry WEDZICHA, Victor NORDIN</b>	117
17	ANALYSIS OF WELDINGS' INCOMPATIBILITY IN CONSTRUCTIONS <b>Magdalena MAZUR, Lenka KUCHARIKOVÁ</b>	129
18	MONITORING THE QUALITY OF LASER CUTTING <b>Rastislav BERNÁT, Zoltán ZÁLEŽÁK, Jozef ŽARNOVSKÝ, Norbert KECSKÉS, Milan PENIAŠKO, Katarzyna MIDOR</b>	137
19	ANALYSIS OF THE IMPACT OF UNSCHEDULED DOWNTIMES IN MACHINE OPERATION ON THEIR AVAILABILITY <b>Jarosław BRODNY</b>	145
20	LABORATORY TESTS OF A SPEED CONTROL SYSTEM FOR ROADHEADER CUTTING HEADS <b>Jarosław JOOSTBERENS, Adam HEYDUK</b>	153
21	A COMPARATIVE ANALYSIS OF THE IMPACT OF CNC MILLER PROGRAMMING ON MACHINING EFFECTS <b>Józef KUCZMASZEWSKI, Paweł PIEŠKO, Magdalena ZAWADA-MICHAŁOWSKA</b>	161

22	CARBIDE MILLING CUTTER BLADES DURABILITY DURING MACHINING OF AL-SI CASTING ALLOY <b>Józef KUCZMASZEWSKI, Paweł PIEŚKO, Magdalena ZAWADA-MICHAŁOWSKA</b>	169
23	ASSESSMENT OF THE RANGE OF DANGER ZONES DETERMINED IN A FUNCTION OF LNG CHEMICAL COMPOSITION <b>Agnieszka KALBARCZYK-JEDYNAK</b>	177

### New Trends and Ideas in Technology and Engineering

24	APPLYING HARMONIC ANALYSIS IN THE MEASUREMENTS OF GEOMETRICAL DEVIATIONS OF CRANKSHAFTS – ROUNDNESS SHAPES ANALYSIS <b>Krzysztof NOZDRZYKOWSKI</b>	185
25	APPLYING HARMONIC ANALYSIS IN THE MEASUREMENTS OF GEOMETRICAL DEVIATIONS OF THE CRANKSHAFTS – SELECTING SUPPORT CONDITIONS <b>Krzysztof NOZDRZYKOWSKI</b>	19
26	THE IDENTIFICATION ACCURACY OF ADDITIONAL WAVE RESISTANCE THROUGH A COMPARISON OF MULTIPLE REGRESSION AND ARTIFICIAL NEURAL NETWORK METHODS <b>Tomasz CEPOWSKI</b>	19
27	APPLYING THE ANTICIPATORY FAILURE DETERMINATION AT A VERY EARLY STAGE OF A SYSTEM'S DEVELOPMENT: OVERVIEW AND CASE STUDY <b>Leszek CHYBOWSKI, Katarzyna GAWDZIŃSKA, Valeri SOUCHKOV</b>	20
28	EXAMPLE OF USING LEAN MANUFACTURING TOOLS IN ASSESSING AND IMPROVING THE PROCESS OF CAR ARM REST PRODUCTION <b>Michał MOLENDĄ, Aneta BIERNOT, Helena CIERNA</b>	2
29	TESTS OF AN INNOVATIVE CONTROLLER DESIGNED TO CONTROL THE POWERED ROOF SUPPORT <b>Dawid SZURGACZ, Horst GONDEK</b>	2
30	MICROBIOLOGICAL RISK ASSESSMENT AND BIOPROCESS ENGINEERING <b>Grażyna PŁAZA, Varenyam ACHAL, Deepika KUMARI</b>	2
31	ADVANTAGES AND DISADVANTAGES OF USING METHANE FROM CNG IN MOTOR VEHICLES IN POLISH CONDITIONS <b>Adam GÓRNIĄK, Katarzyna MIDOR, Jan KĄŻMIERCZĄK, Wojciech KANIĄK</b>	2
32	SYSTEMS ENGINEERING IN SMES – A CASE OF RFID SOLUTIONS PROVIDER <b>Aleksander BUCZACKI, Bartłomiej GLĄDYSZ</b>	2
33	THE USE OF TRIZ SU-FIELD MODELS IN THE PROCESS OF IMPROVING THE INJECTOR OF AN INTERNAL COMBUSTION ENGINE <b>Leszek CHYBOWSKI</b>	2
34	HIGHLY EFFICIENT TECHNOLOGY FOR MANUFACTURING OF SPUNLACE NON-WOVEN FABRIC IN THE COMPANY NOVITA S.A. POLAND – DESCRIPTION AND CHARACTERISTIC OF THE R&D ACTIONS <b>Michał SAŚIADEK, Waldemar WOŻNIAK, Bartłomiej JANKOWSKI, Urszula BŁĄSZCZYK, Roman STRYJSKI</b>	2
35	REVIEW OF THE HARD-FACING TECHNOLOGY APPLICATION FOR REPARATION OF THE RESPONSIBLE PARTS IN VARIOUS BRANCHES OF INDUSTRY <b>Vukić LAZIĆ, Dušan ARSIĆ, Milan MUTAVDŽIĆ, Ružica NIKOLIĆ, Jozef MEŠKO, Ljubica RADOVIĆ, Nada ILIĆ</b>	2
36	INNOVATIVE ADAPTIVE CONTROL OF MATERIAL FATIGUE TEST MACHINES USING AN MCS CONTROLLER <b>Adam HEYDUK, Krystian KALINOWSKI, Roman KAULA, Joachim PIELOT</b>	2
37	APPLICATION OF ARDUINO MODULE TO RESEARCH IN SURFACE PHYSICS <b>Andrzej NOWROT, Barbara SOLECKA</b>	2
38	A FAST METHOD OF IDENTIFYING RECHARGEABLE BATTERIES CONDITION AND DEFECTS <b>Krzysztof KULIŃSKI, Andrzej NOWROT</b>	2
39	THE NEW WAY OF MONITORING THE PRODUCTION ENVIRONMENT WITH THE APPLICATION OF AUGMENTED REALITY AND ARTIFICIAL INTELLIGENCE <b>Andrzej SZAJNA, Janusz SZAJNA, Roman STRYJSKI, Josef BASL, Jarosław BRODNY</b>	2
40	APPLICATION OF INDUSTRIAL AUTOMATICS SYSTEMS FOR MONITORING OF OPERATIONAL STATES OF MACHINES <b>Jarosław BRODNY</b>	2

**Vukić Lazić,  
Dušan Arsić**  
University of Kragujevac, **Serbia**

**Milan Mutavdžić**  
High Technical School, Leposavić, **Serbia**

**Ružica Nikolić  
Jozef Meško**  
University of Žilina, **Slovak Republic**

**Ljubica Radović  
Nada Ilić**  
Military Technical Institute, Belgrade, **Serbia**

**Abstract:** This paper deals with the problem of defining the optimal procedure for reparation of the machine parts of large dimensions and complex shapes. The procedure consists of establishing the causes of the part's damages, definition of the reparation technology, with selection of its parameters and ways of execution. The reparation is done by hard-facing, with heat treatment that consists of preheating, additional heating and the post hard-facing tempering. The process parameters' selection includes choosing the right filler metal(s), ways and order of depositing the hard-faced layers, ways of reaching and maintaining the preheating temperatures, checking of the base metal's chemical composition and mechanical properties and deciding on the post-process heat and mechanical processing of the executed hard-facing. The executed reparation of the forging hammer's mallet, presented in details, serves as an example how the reparation can successfully serve as a substitute for procuring the new part and thus producing the savings both directly in lower costs and indirectly in shortening the down-time of the damaged part operation.

**Keywords:** regeneration, hard-facing, friction, wear, machine parts

## **1. INTRODUCTION**

Investigation of causes of machines' and devices' damages has established the fact that in more than 50% of cases damages appear due to the tribological processes in regular exploitation conditions and thermal fatigue (Lazić, 2001). This is why for design of regeneration technology it is necessary to know the possible wear mechanisms of the coupled elements. There, one has to keep in mind that, besides for regeneration of parts worn in normal operation, the hard-facing is used for regeneration of parts that suffered accidental fractures, as well as for the new cast parts manufactured with flaws. Hard-facing of the new parts is gaining an increased significance. The necessary hardness of the surface layers of those new parts is achieved by depositing the hard alloys, instead of by the classical heat treatment methods. All the aforementioned has contributed for the hard-facing to play the important role in the so-called advanced technologies.



The responsible parts of machines, assemblies or devices are usually made of expensive alloys, thus by reparation, besides the shortening the down-times due to repairs, the savings are achieved both in the expensive base metal and in machining the parts to final dimensions. Economically the most justified is to regenerate the damaged parts by some of the welding methods. In the majority of cases, the criterion for performing the reparation is that the regeneration costs of the part do not exceed the price of manufacturing the new part. This is particularly important for the parts of large dimensions and in the batch production, while for the unique machines and devices the reparation is done regardless of the costs.

## 2. BASIC CAUSES OF MACHINE SYSTEMS DAMAGES

The notion of wear implies the loss of material from the contact surfaces caused mainly as a result of the mechanical forces action. Chemical processes, which accompany these phenomena, can sometimes be the basic cause of wear due to action of corrosion. Wear is a consequence of friction or common action of friction, thermal, chemical, electrochemical and other factors, on elements of the tribo-mechanical system, i.e. on their contact surfaces. Loss of material causes change of the shape and characteristics of the mechanical system elements, thus causing change of their functional characteristics.

In considering the wear, the factors that are primarily considered are those that are dominant in the given working conditions, like: material, quality and properties of the contact surfaces, properties of the relative motion between the contact surfaces, magnitude of loading, quantity and properties of particles created during the wear, etc. Thus, wear influences the change of shape and characteristics of the system's elements, where one of the wear types can be dominant: abrasive, adhesive, erosive, cavitation, fatigue, vibrational and combined.

## 3. REVIEW OF THE HARD-FACING PROCESSES

Hard-facing, whether *manufacturing* or *reparatory*, can be techno-economically justified only with the rational selection of the hard-facing process, filler metal, technology and the control methods.

All the welding by melting processes can be applied for the hard-facing: *gas, manual arc, in protective atmosphere, powder or dross shielded, plasma, electro-vibration*; in the recent times hard-facing is also done by *electron beam, laser beam* and *friction*.

During the hard-facing, in majority of processes, it is necessary to take into account the degree of mixing, which is the biggest in the first layer, then significantly smaller in the second and third layer, what automatically implies the necessity of the multi-layer hard-facing.

The application area of hard-facing is very broad; hard-faced are various tools, gears, crack-shafts, internal combustion engines, working parts of the construction machinery for soil processing, parts of the transportation means, rollers of the rolling mills, coating of vessels in the chemical industry etc. It is also applied for correction of the casting flaws on the cast pieces of steel, iron, aluminum, brass, bronze, etc.

The hard-facing is based on deposition of the filler metal layers, which are usually of the different chemical composition than the base metal for the cases of regeneration, and of the approximately the same composition for correcting the casting flaws, or when the molds and forging dies are repaired. The deposited coating, i.e. the hard-faced layer, is not taken into account in dimensioning the corresponding structural parts, i.e. it is not considered as the carrying cross-section.

*Manual arc hard-facing (MAG)* is still the dominant procedure, both for the reparatory operations and for depositing the hard-faced coatings on the working surfaces of tools and parts.

In reparation of the worn parts, or repeated hard-facing, it is necessary of remove the damaged metal by machining, especially if there are cracks, which can act as the stress concentrators. This hard-facing procedure is applied for parts of steel, cast iron, Cu and Al and Ni alloys etc. In the majority of cases, the MAG welding can be executed without preheating. However, in

the cases of thick hard-faced layers deposition over the massive steel substrate with the carbon content above 0.35%, the preheating is mandatory. However, the preheating is not necessary when the austenitic Mn steel is hard-faced, which hardens by the complex mechanisms under the impact cold workloads. This steel and its thin sheets, are hard-faced by the short layers, with minimum heat input and fast cooling of the deposited layers.

For materials that are prone to forming of cracks in the HAZ, the short layers are hard-faced in the width equal to 1 to 2 electrode diameters, what reduces the "dissolution" of the filler metal, inherent stresses and deformations. However, for materials of good weldability, the hard-faced layers are wide and deposited with high intensity current. When the large areas are hard-faced by hard alloys, it is recommended to deposit the plastic inter-layer, of the Ni or austenitic electrodes, in the form of separated welds. The following layers are then executed with the maximum allowed intensity current, with welds that overlap. In general, the plastic inter-layer is recommended also in the cases of the bigger difference in thermo-physical properties between the hard-facing alloy and the base metal, as well.

Hard-facing of cylindrical surfaces can be done by depositing the longitudinal layers, or in the case of larger parts by the circular welds. Usually, for axles and shafts, the first hard-faced layers are deposited to the diametrically opposite sides in order to balance the thermal deformations (Jovanović et al. 1996; Lazić et al., 2001).

#### 4. BASIC PRINCIPLES FOR SELECTION OF THE FILLER METALS

In the majority of cases, the filler metal for hard-facing is selected based on the required properties of the hard-faced part and available equipment. In the case when the heat treatment cannot be executed after the hard-facing, the required properties of the hard-faced layers can be achieved by adequate selection of the filler metal's chemical composition. In the case that the device operates in the conditions of the increased corrosive actions, the filler metals are being selected exclusively based on the chemical composition, which depends on the corrosion type; in the cases of parts exposed to friction forces, the problem of the filler metal selection is significantly more complex. However, hardness and the chemical composition cannot be the only criteria for estimate of the coating material adequacy. A brief review of the most frequently used filler metals, resistant to wear, is presented in (Lazić et al., 2001; Arsić et al., 2015). The filler metals, resistant to wear and corrosion are grouped into six classes: steels, white cast irons, tungsten carbides, cobalt alloys, nickel alloys and copper alloys.

#### 5. DETERMINATION OF THE OPTIMAL TECHNOLOGY FOR REPARATION OF THE FORGING HAMMER'S MALLET

##### 5.1. Analysis of the hammer mallet's base metal

It was established, by chemical analysis, that the base metal is the low-alloyed tempering steel, which corresponds to steel 34CrNiMo6 (DIN). The percentage share of individual elements is given in Table 1, (Lazić et al., 2009).

**Table 1**  
**Prescribed and analyzed chemical composition of (34CrNiMo6) steel**

Chemical composition, %						
	C	Si	Mn	Cr	Ni	Mo
Prescribed	0.30-0.38	0.15-0.40	0.40-0.70	1.40-1.70	1.40-1.70	0.15-0.30
Analyzed	0.35	0.27	0.45	1.25	1.64	0.22

##### 5.2 Weldability estimate

This steel belongs into a group of poorly weldable materials; besides the increased content of carbon ( $C = 35\% > 25\%$ ), it also contains the alloying elements (Cr, Mo, Ni), which are improving the mechanical properties, but worsening the weldability. The weldability was evaluated according to the value of the chemically equivalent carbon (CE), (Jovanović et al.

1996). Since the calculated value exceeded the recommended limit (CE = 45%) and taking into account the thickness of the part to be repaired, it was obvious that this steel must be preheated, additionally heated and subjected to high tempering during the welding.

The preheating temperature was calculated according to the Seferian formula for the thickness over 240 mm, as 350°C, (Jovanović et al. 1996). Since the preheating temperature cannot not be higher than  $M_s$  temperature (about 310 °C), the adopted preheating temperature was  $T_p = 300 \pm 10^\circ\text{C}$ . The previous experiences of these authors in reparation of the mallets have shown that the local preheating does not have any effect on massive parts, due to the "heat sink", that appears, (Lazić et al., 2009; 2014; 2016). This is why the whole mallet, of the 6000 kg mass, after elimination of cracks, is being preheated up to the calculated temperature. The additional heating is often done, since it is necessary to maintain the initial preheating temperature.

### 5.3 Selection of the filler metal

The basic electrode GALEB 70 ( $\varnothing 3.25$  and  $\varnothing 4$  mm) was used for coating the groove, while for the groove filling the electrode PIVA 352 was applied. To increase the surface hardness of the sliding-guides zones, it was necessary to execute the several surface layers by the E DUR 300 electrode, Table 2. The recommended welding parameters are given in Table 3. Electrodes drying rate was 400°C/1h.

### 5.4 Selection of the reparation technology

Prior to hard-facing, it is necessary to reach the crack tip by machining, i.e. to perform the "releasing" of all the flaws and create the optimal groove for welding. It is recommended to design the groove with the minimal weld's volume. It is also agreed to reach the "healthy" base metal by mechanical machining, thus creating the surface without cracks to which the missing portion of the mallet's volume would be hard-faced.

**Table 2**  
Properties of the filler metals (Catalogues of electrode manufacturers)

Electrode mark	Chemical composition, %						Current type	Mechanical properties of the hard faced layer				Hardness HB
	C	Si	Mn	Cr	Ni	Mo		$R_m$ MPa	$R_{eH}$ MPa	$A_5$ %	KV J	
GALEB 70**	0.08	0.70	1.50	-	0.7	0.20	= (+)	640-710	> 520	> 22	> 125 +20°C	-
PIVA 352 B*	0.08	0.5	0.85	2.3	-	1.0	= (+)	640-720	540-620	19-26	90-140	-
E DUR 300**	0.18	-	1.30	1.2	-	-	= (+)	-	-	-	-	280-330

\*) Electrode manufacturer FEP Plužine, Montenegro.  
\*\*) Electrode manufacturer SŽ Jesenice, Slovenia.

The heat input influence on the output properties of the hard-faced samples was analyzed, with help of the TTT diagrams for this particular steel. Calculating the cooling time between 800°C and 500°C ( $t_{8/5}$ ), one can estimate the structure and hardness in the most critical zone – the HAZ. By entering this time into the TTT diagram, the hardness and structures were estimated and results are presented in Table 4 (Jovanović et al., 2001; Lazić, 2001; Lazić et al., 1997; 2016).

**Table 3**  
Recommended parameters of welding/hard-facing


Sample #	Electrode properties				Heat treatment	
	Mark	Diameter mm	Input current A	Current type	Preheating temperature $T_{p1}$ , °C	Tempering temperature $T_{temp}$ , °C
1	GALEB 70	3.25	110-130	= (+)	300	650
		4.0	130-160			
		5.0	170-200			
2	PIVA 352	3.25	100-130	= (+)	300	650
		4.0	140-180			
		5.0	180-230			
3	E DUR 300	3.25	100-135	= (+)	300	650
		4.00	130-170			
		5.00	180-220			

**Table 4.**  
Parameters of the MAG hard-facing and estimated properties of the HAZ

Electrode diameter mm	Hard-facing current A	Voltage V	Hard-facing rate cm/s	Input energy J/cm	Cooling time $t_{0.5}$ s	HAZ micro-structure	HAZ hardness HV
3.25	110	24.5	≈ 0.124	17387	17.3	Martensite	573 - 580
4.0	170	27	≈ 0.160	22950	26.3	Martensite	573 - 580
5.00	200	28	≈ 0.169	26509	32.6	Martensite	573 - 580

Based on the obtained results, it was concluded that the unfavorable structure and high hardness are obtained, regardless of the input energy. This is why it was necessary to execute the tempering after the hard-facing, so that the brittle martensite structure should be transformed into more favorable structures of higher plasticity.

After the theoretical considerations and prior to actual repair of the damaged mallet shown in Figure 1, the model investigations by hard-facing the samples of the similar material as the mallet's, were performed. The samples were preheated, then hard-faced by the adequate technology and afterwards tempered with different cooling rates. The laboratory tests were performed on the hard-faced samples and thus the optimal hard-facing technology was defined, that should be then applied for reparation of the mallet itself, Figure 1.

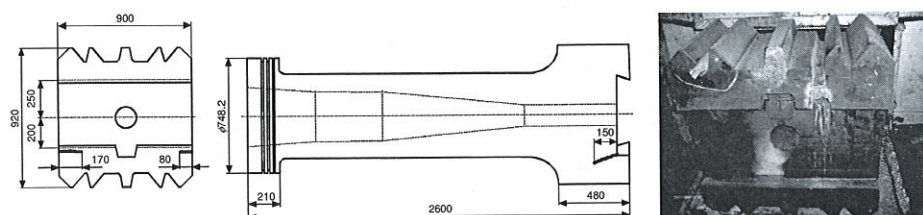

**Fig. 1. Forging hammer's mallet with noticed cracks and appearance of the mallet during the reparation**

It should be first preheated according to the precisely prescribed procedure. The unheated part is placed into the furnace, then heated with it until the desired temperature is reached and then kept at that temperature for a certain time. The cleaned part of the mallet that is to be hard-faced, is then pulled out from the heat-treatment furnace, Figure 1, and then repaired. The temperature must be maintained at the attained level during the whole process by the additional heat sources. The special tools, the "positioners" are used to enable that the hard-facing is done in the natural position – the "H" position.

### 5.5 Order of the operations during the mallet repairation

- Prior to hard-facing, the basic electrodes should be dried according to manufacturer's recommendations;
- The root layers should be deposited by electrodes of the smaller diameter, while for the welds and covering layers should be used the larger diameter electrodes;
- The adequate block-sequences technology should be applied, both for the filling the groove and executing the final layers;
- Freshly deposited layers should be forged-out within the adequate temperature interval, by application of the special tool with the rounded tip;
- After each pass, the dross should be hammered-out and removed by the steel brushes;
- The preheating temperature should be controlled by the thermo-chalks or the special digital instrument with a thermocouple, or the contactless thermometer;
- The additional heating should be used for maintaining the required temperature;
- After the executed repairation and cooling, the mallet should be subjected to tempering, which consists of gradual heating up to the set temperature, heating-through at that temperature and slow cooling within the furnace down to the room temperature. The complete temperature cycles is shown in Figure 2, (Lazić et al., 2009).

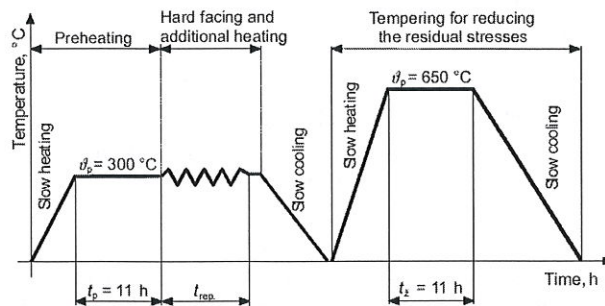


Fig. 2. The complete temperature cycles of the mallet's repairation

After the completed repairation cycle, the mallet is subjected to machining in order to restore its initial dimensions and shape. The whole process of the mallet repairation, Figure 3, that lasted several weeks, together with some previous experience of repairing the mallets and presses (Lazić et al., 2009; 2016), enabled obtaining the physical model of this complex procedure, which can serve as the guide-line for the future repairation processes of parts of the similar shape and dimensions. However, regardless of this fact, each individual repairation must be approached as a very responsible and complex problem, definitely not as a routine job. By application of the new knowledges, the optimal technologies and filler metals, it is realistic to expect multifold positive effects of the repairation processes, both direct and indirect ones.

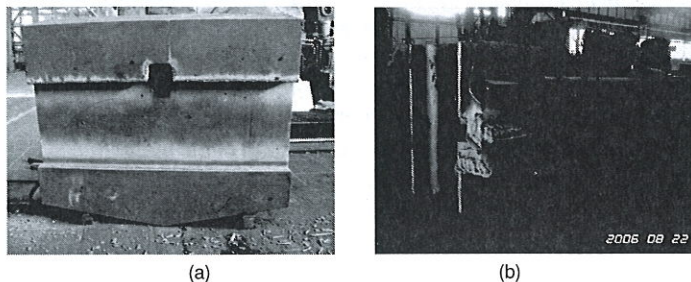


Fig. 3. Appearance of individual zones of the repaired mallet:  
(a) the hard-faced guides and (b) repaired teeth

## 6. CONCLUSIONS

The successful reparation by hard-facing is only possible if that task is undertaken after the detailed analysis of causes of damages and selection of the technological parameters of the process. To obtain the reparation model it is necessary to perform the numerous experimental and model investigations, when the influence of the input parameters changes on the output properties of the executed operations are monitored. This is primarily related to the heat input and the cooling rate in the critical temperature interval.

The proposed reparation model, based on the previously established rank of individual parameters influences, was practically verified by the successful reparation of parts of various machine systems. In addition, this reparation model enables selection of the procedure and technology for hard-facing according to the required working conditions of the hard-faced parts and devices.

## ACKNOWLEDGEMENT

This research was partially financially supported by European regional development fund and Slovak state budget by the project "Research Centre of the University of Žilina" and by the Ministry of Education, Science and Technological Development of Republic of Serbia through grants TR35024 and TR33015.

## REFERENCES

- Arsić, D., Lazić, V., Samardžić, I., Nikolić, R., Aleksandrović, S., Djordjević, M., Hadzima, B. (2015). Impact of the hard facing technology and the filler metal on tribological characteristics of the hard faced forging dies. *Technical Gazette*, 22(5), pp. 1353-1358.
- Catalogues: Thyssen Marathon Edelmetall - Vosendorf, FEP-Plužine, Elvaco-Bijeljina, Železarna Jesenice-Fiprom, Bohler-Kapfenberg, Messer Griesheim-Frankfurt am Main, Esab-Göteborg, Lincoln Electric, USA, Atlas zur Wärmebehandlung der Stähle.
- Jovanović, M., Adamović, D., Lazić, V. (1996). *Welding technology, handbook*. Faculty of Engineering, University of Kragujevac, Kragujevac (in Serbian).
- Lazić, V., Jovanović, M., Rajačić, D., Josifović, D., Adamović, D. (1997). Surfacing of the truck lift hook. *Welding and welded structures*, 42(3), pp. 159-164.
- Lazić, V. (2001). Optimization of the hard-facing process from the tribological aspects of the hard-faced layers and residual stresses. PhD. Faculty of Mechanical Engineering, Kragujevac.
- Lazić, V., Jovanović, M., Josifović, D., Adamović, D., Ristović, J., Nedeljković, B. (2001). Influence of the heat treatment after the hard-facing on the working characteristics of the hard-faced forging tools. *Welding and welded structures*, 46(1-2), pp. 5-11.
- Lazić, V., Jovanović, M., Adamović, D., Josifović, D., Ratković, N. (2006). Development and application of welding technologies for regeneration of damaged working parts of forging presses and hammers. In: *Welding and Joining Technologies for a Sustainable Development and Environment*, Timisoara, Romania, pp. 341-346.
- Lazić, V., Sedmak, A., Aleksandrović, S., Milosavljević, D., Čukić, R., Grabulov, V. (2009). Reparation of damaged mallet for hammer forging by hard facing and weld cladding. *Technical Gazette*, 16(4), pp. 107-113.
- Lazić, V., Čukić, R., Aleksandrović, S., Milosavljević, D., Arsić, D., Nedeljković, B., Djordjević, M. (2014). Techno-Economic Justification of Reparatory Hard Facing of Various Working Parts of Mechanical Systems. *Tribology in Industry*, 36(3), pp. 287-292.
- Lazić, V., Arsić, D., Nikolić, R., Mutavdžić, M., Meško, J. (2016). Reparation by hard facing of the damaged secondary stone crushers. *Manufacturing Technology*, 16(2) pp. 375-380.